


# Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: Y. Shin, A. panigrahi, M. boyes, X. Just-Baringo, M. Zarattini, Y. chen, X. Liu, G. A. Morris, E. Prestat, K. Kostarelos, S. Vranic, I. Larrosa and C. Casiraghi, *Faraday Discuss.*, 2019, DOI: 10.1039/C9FD00114J.

## Enhanced Liquid Phase Exfoliation of Graphene in Water Using an Insoluble Bis-Pyrene Stabiliser

View Article Online

DOI: 10.1039/C9FD00114J

Yuyoung Shin<sup>1</sup>, , Xavier Just-Baringo<sup>1</sup>, Matthew Boyes<sup>1</sup>, Adyasha Panigrahi<sup>1</sup>, Marco Zarattini<sup>1</sup>, Yingxian Chen<sup>2</sup>, Xinyun Liu<sup>3</sup>, Gareth Morris,<sup>1</sup> Eric Prestat<sup>3,4</sup>, Kostas Kostarelos<sup>2</sup>, Sandra Vranic<sup>2</sup>, Igor Larrosa\*<sup>1</sup>, Cinzia Casiraghi\*<sup>1</sup>

<sup>1</sup>*Department of Chemistry, University of Manchester, Oxford Road, Manchester, M13 9PL*

<sup>2</sup>*Nanomedicine Lab, National Graphene Institute and Faculty of Biology, Medicine & Health, AV Hill Building, University of Manchester, Manchester, M13 9PT*

<sup>3</sup>*Department of Materials, University of Manchester, Oxford Road, Manchester, M13 9PL*

<sup>4</sup>*SuperSTEM Laboratory, SciTech Daresbury Campus, Daresbury, WA4 4AD, UK*

### Abstract:

Stabilisers, such as surfactants, polymers and polyaromatic molecules, offer an effective way to produce graphene dispersions in water by Liquid Phase Exfoliation (LPE), without degrading the properties of graphene. In particular, pyrene derivatives provide better exfoliation efficiency than traditional surfactants and polymers.

A stabiliser is expected to be relatively soluble in order to disperse hydrophobic graphene in water. Here, we show that exfoliation can also be achieved with insoluble pyrene stabilisers if appropriately designed. In particular, bis-pyrene stabilisers (BPSs) functionalised with pyrrolidine provide higher exfoliation efficiency and percentage of single layers, as compared to traditional pyrene derivatives, under the same experimental conditions. This is attributed to the enhanced interactions between BPS and graphene, provided by the presence of two pyrene binding groups. This approach is therefore attractive not only to produce highly concentrated graphene, but also to use graphene to disperse insoluble molecules in water. The enhanced adsorption of BPS on graphene, however, is reflected in higher toxicity towards human epithelial bronchial immortalized cells, limiting the use of this material for biomedical applications.



## Introduction

Graphene, a single layer of graphite, shows great potential for numerous applications due to its outstanding properties, including extreme mechanical strength and exceptionally high electronic and thermal conductivity.<sup>1</sup> Out of all graphene's synthesis techniques, Liquid-Phase Exfoliation (LPE)<sup>2</sup> allows for mass-scalable, cost-effective and versatile production of graphene formulations suitable for a wide range of practical uses, ranging from composites to biomedical applications.<sup>1,3-5</sup>

Liquid Phase Exfoliation relies on the use of solvents with surface tension comparable to that of graphene.<sup>2</sup> Thus, *N*-methyl-2-pyrrolidone (NMP) is typically the solvent of choice.<sup>2</sup> However, its toxicity, high cost and boiling point do not make it an ideal solvent. Water is a low cost and friendly solvent, required in many applications. However, in order to effectively exfoliate graphite in water, the graphene surface needs to be altered, either covalently or non-covalently.<sup>6-8</sup> The use of stabilisers offers an effective method to functionalise the material without introducing defects, hence maintaining the intrinsic properties of graphene, while allowing dispersability in water.<sup>9-11</sup> Different types of stabilisers, including surfactants<sup>9,12-14</sup>, polymers<sup>15-17</sup> and polyaromatic molecules<sup>10,18,19</sup> have been investigated.

Stabilisers are typically amphiphilic, *i.e.* they have a hydrophobic binding group, which adsorbs onto the graphene surface through van der Waals interactions, and a hydrophilic group, which prevents re-stacking of exfoliated graphene nanosheets through steric hindrance and/or electrostatic stabilisation.<sup>10,20</sup> Out of all stabilisers, pyrene derivatives have been shown to be very effective at exfoliating graphite, when compared to typical surfactants and polymers, due to the effective adsorption of pyrene on graphene through  $\pi - \pi$  interactions.<sup>10,11,21-23</sup> In particular, in our group, we have extensively used 1-pyrenesulfonic acid sodium salt (PS1) to obtain biocompatible and inkjet-printable graphene dispersions in water.<sup>4,21,24</sup>

Despite the wide use of pyrene derivatives as stabilisers, the effective mechanisms leading to exfoliation are very poorly understood. Seminal works have shown that not all pyrene derivatives are effective exfoliating agents.<sup>10,11,25</sup> Exfoliation efficiency, as defined by the concentration of graphene, depends strongly on many factors, such as types and number of functional groups, and the charge distribution in the stabiliser, which determine the thermodynamics of the interaction between the stabiliser and graphene, *e.g.* the adsorption of the pyrene binding group on the graphene surface, the affinity of the functional groups for the solvent medium, and the effectiveness of deterrence of re-stacking of graphene sheets.<sup>9,10,26-28</sup> Since the affinity of the functional groups for the solvent medium of the functional groups is

View Article Online  
DOI: 10.1039/C9FD00114J



one of the key parameters, stabilisers with relatively good aqueous solubility have been used up to now.

View Article Online

DOI: 10.1039/C9FD00114J

In this work, we show that pyrene derivatives with extremely low solubility can be exceptionally efficient as exfoliating agents, contradicting the common assumption that an effective stabiliser needs to be soluble in water. A bis-pyrene stabiliser (BPS), functionalized with a pyrrolidine central group (**Scheme 1**), was designed and synthesized *ad hoc* for this study. Its exfoliation efficiency was compared to that of two pyrene derivatives with the same functional group: one with longer linking chains between the pyrene binding groups and the functional group (LBPS) and the other with a mono-pyrene binding group (MPS) (**Scheme 1**). BPS has been found to be insoluble in aqueous media, *i.e.* the aqueous solubility of BPS is under the detection limit of NMR. Despite this the BPS molecule showed exfoliation efficiency up to 3-5 times higher than that obtained with PS1 or MPS. Furthermore, the graphene dispersion prepared with BPS showed a higher percentage of single layer graphene (SLG), compared to PS1. The enhanced exfoliation efficiency of BPS, compared to the other stabilisers, is attributed to the higher interaction strength between BPS and graphene, driven by stronger  $\pi$ - $\pi$  interactions due to the presence of two pyrene binding groups in BPS, and the insolubility of BPS in water (as confirmed by  $^1\text{H}$  NMR). Finally, cytotoxicity studies on the graphene dispersions prepared with BPS show the toxicity of graphene to be dependent on the initial BPS concentration, whereas the graphene dispersion prepared with MPS showed no cytotoxic effect. Since the sizes of the nanosheets prepared with BPS and MPS are comparable, the difference in toxicity is attributed to the presence of two pyrene binding groups in BPS, which may affect how these molecules assemble on graphene, in particular at high BPS concentrations.

## Methods

### Materials

#### Preparations of pyrene derivatives

The details of the synthesis routes for the pyrene stabilisers and all characterisation methods used for identification of the structure and purity of the compounds are given in the Supplementary Information.

#### Preparations of graphene dispersions

Natural graphite crystals were provided by Graphexel Ltd. Graphene dispersions were prepared by LPE in water following the protocol developed in previous works.<sup>4,21,29</sup> In detail, 300 mg of graphite and varying amount of stabilisers were added to 100 mL of de-ionized (DI) water. The



mixture was then sonicated at 600W for 7 days using a Hilsonic bath sonicator. Afterwards, un-exfoliated graphite was removed by two-step centrifugation (Sigma 1-14k refrigerated centrifuge) at 3500 rpm (903 g) for 20 min. After each centrifugation step, the supernatant containing graphene in water was collected. For cytotoxicity studies, the graphene dispersions prepared were further centrifuged at 15000 rpm (16 600 g) for 60 min to increase the concentration further by collecting the sediment and re-dispersing in a smaller volume of DI water. In the case of the graphene dispersions prepared with BPS, the supernatant was also collected for characterisation. In the case of the graphene dispersions prepared with MPS, the second centrifugation step was repeated twice to remove excess pyrene from the solution.

## Characterization

### UV-Vis Spectroscopy

The concentration of graphene dispersed in the solution was determined using UV-Vis spectroscopy. The UV-Vis spectrum of graphene appears flat and featureless in the visible-IR region,<sup>2</sup> so the absorption is measured at 660 nm for estimation of the graphene nanosheet concentration using the Beer-Lambert law. Despite the extensive work done towards accurately estimating the absorption coefficient, this is still the subject of considerable debate.<sup>30</sup> In this study, an absorption coefficient of 2460 L/g m was used for estimating the graphene concentration.<sup>9,12,31</sup> A Perkin-Elmer I-900 UV-Vis-NIR spectrophotometer was used to acquire the spectra.

### Zeta Potential Measurements

Electrophoretic mobility ( $\mu$ ) was measured using a ZetaSizer Nano ZS (Malvern Instruments, UK) after dilution of samples with water in the folded capillary cells (Malvern Instruments, UK). Default instrument settings for water-based system and automatic analysis were used for all measurements, which were performed at 25 °C and at the natural pH. The equipment software automatically converted the mobility  $\mu$  to zeta potential ( $\zeta$ ) values by Henry's equation:  $\mu = 2\varepsilon\zeta F(\kappa a)/3\eta$  where  $\varepsilon$  is dielectric constant,  $\eta$  is the solution viscosity and  $F(\kappa a)$  is Henry's function, approximated to the value of 1.5 using the Smoluchowski approximation for polar media, valid for dispersed particles of any shape including plate-like particles.<sup>32</sup> All values for samples are mean  $\pm$  standard deviation (SD), calculated from triplicate measurements.

### Atomic Force Microscopy (AFM)

View Article Online  
DOI: 10.1039/C9FD00114J

Faraday Discussions Accepted Manuscript



A Bruker Atomic Force Microscope (MultiMode 8) in Peak Force Tapping mode, equipped with ScanAsyst-Air tips, was used to determine the lateral size distribution of the flakes. The sample was prepared by drop casting the solution on a clean silicon substrate; areas of 10 to 400  $\mu\text{m}^2$  were scanned and typically 200 or more flakes were selected for lateral size analysis. Lateral dimension and thickness distributions of graphene nanosheets were carried out using Gwyddion scanning probe microscopy data processing software.

View Article Online  
DOI: 10.1039/C9FD00114J

### **Transmission Electron Microscopy (TEM)**

TEM imaging was performed using a FEI Talos 200X operating at an acceleration voltage of 200 kV, and TEM images were acquired using a FEI CETA CMOS (complementary metal-oxide semiconductor) camera. TEM samples were prepared by dip coating the graphene dispersions either on a lacey carbon copper grid or on a 3 nm ultrathin carbon film supported on lacey carbon copper grid. Measurements of the numbers of layers were performed by High Resolution TEM (HRTEM) imaging of free-standing graphene flakes on the lacey carbon film. The graphene dispersion deposited on ultrathin carbon film was used for the measurement of the lateral size of the graphene flakes.

### **Raman Spectroscopy**

Raman measurements were performed using a Renishaw Invia Raman spectrometer equipped with a 514.5 nm excitation line and 2.0 mW laser power. Graphene dispersions were drop-cast onto silicon substrates and measurements were performed on isolated and individual flakes. The Raman spectra were taken with a 100 $\times$  NA0.85 objective lens and 2400 grooves/mm grating. Typically, 30-50 flakes were measured for each sample. The Raman peaks were fitted with a Lorentzian lineshape. The Raman analysis was performed using a qualitative protocol developed for graphene produced by LPE in our group.<sup>13,26,27,33,34</sup> In detail, the shape of the 2D peak is used for determination of the thickness distribution. The 2D peak is fitted with a single Lorentzian lineshape, and by evaluating the fit residual ( $R^2$ ), the spectrum is attributed to a single-layer graphene (SLG), or few-layer sheets (FLG), or to graphitic material (>10 layers with AB stacking) in the following way. A single symmetric 2D peak with  $R^2 > 0.987$  is attributed to the spectrum of a SLG; a single asymmetric peak with  $R^2 < 0.987$  is attributed to FLG; and graphitic material is identified by its characteristic peak shape, characterized by a low-wavenumber shoulder.

### **Nuclear Magnetic Resonance**

All nuclear magnetic resonance (NMR) spectra reported were acquired at a nominal temperature of 25  $^\circ\text{C}$  using a VNMR5 500 spectrometer operating at 499.826 MHz for  $^1\text{H}$ . The standard  $^1\text{H}$  spectrum was acquired in 1.3 h using 90 $^\circ$  pulses, a spectral width of 10 kHz, 32768



complex data points, and a recycle time of 3.4 s. The diffusion-ordered spectroscopy (DOSY) data were acquired in a total time of 11 h using the Oneshot pulse sequence<sup>35</sup>, with a spectral width of 19.8 kHz, a recycle delay of 5 s, and 32768 complex data points, and processed with the manufacturer's VnmrJ software. The Oneshot pulse sequence used a total diffusion-encoding gradient pulse duration of 2 ms (*i.e.* two encoding and two decoding pulses, each of 1 ms duration), a diffusion time of 0.1 s, and 8 diffusion-encoding gradient amplitudes ranging from nominal values of 6 to 54 G/cm in equal increments of gradient squared. The graphene dispersion used for the DOSY experiment was produced via the same LPE process as the rest of this study. Exfoliation of 60 mg of graphite with 12 mg of the BPS in 20 mL of D<sub>2</sub>O allowed the production of a dispersion with a final concentration of 0.8 mg/mL.

### Cell culture

Human epithelial bronchial immortalized cells (BEAS-2B, CRL-9609, ATCC, LGC standards, UK) were maintained in RPMI-1640 cell culture medium (Sigma-Aldrich), supplemented with 10% foetal bovine serum (FBS) (Gibco, Thermo Fisher Scientific), 1000 units penicillin, and 1 mg/mL streptomycin (Sigma-Aldrich) at 37 °C in a humidified 5% CO<sub>2</sub> incubator. Cells were subcultured when reaching 80% confluence, with 0.05% trypsin-EDTA (Sigma-Aldrich), and 10% FBS was used to stop the activity of trypsin-EDTA.

### Treatment of the cells


BEAS-2B cells were seeded in P12-well plates (Corning, Costar, Sigma-Aldrich) in complete RPMI medium at 37°C in a humidified 5% CO<sub>2</sub> incubator for 24 h. After 24 h, BEAS-2B cells reached confluence of ~80 % and were treated with the graphene dispersions prepared with BPS at 0.2 mg/mL, BPS at 0.6 mg/mL, BPS at 1.0 mg/mL and MPS at 0.4 mg/mL (25, 50, 75 and 100 µg/mL, 1 mL/well) in serum-free RPMI medium for 4 h. Following 4 h of incubation, FBS (100 µL/well) was added and the cells were further incubated for additional 20 h. BEAS-2B cells were washed (RPMI w FBS, 1 mL/well) before analysis with a ZEISS Primovert microscope.

## Results and discussion

### Synthesis of pyrene derivatives

In a general synthetic approach, the stabilisers were synthesised via alkylation of pyrrolidine **2a-b** using the parent (1-pyrenyl)boromoalkane **1a-b** for MPS or two consecutive alkylations for BPS and LBPS.



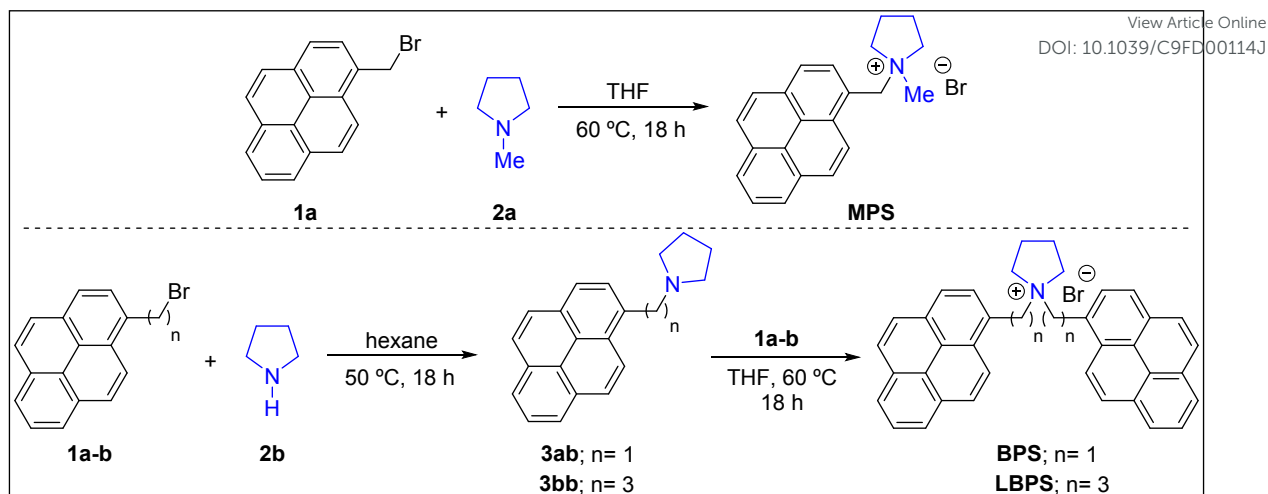

**Scheme 1** General schematic plan for synthesis of the pyrene stabilisers

*Amination of (1-pyrenyl)bromoalkane:* To a vial charged with a stirring suspension of (1-pyrenyl)bromoalkane **1a-b** (1.0 equiv) in dry hexane (1.20 mL) at 0 °C was added secondary amine substrate (4.0 equiv). The reaction mixture was stirred at 50 °C for 18 h. The crude product was cooled down to room temperature and dissolved in CH<sub>2</sub>Cl<sub>2</sub> (50 mL) and washed with saturated aqueous NaHCO<sub>3</sub>. The aqueous layer was extracted with CH<sub>2</sub>Cl<sub>2</sub> (2 × 50 mL) and the combined organic fractions were dried (MgSO<sub>4</sub>) and concentrated under vacuum to afford the corresponding amine products **3ab-bb**.

*Preparation of BPS:* The crude secondary amines **3ab/3bb** or *N*-methylpyrrolidine **2a** were stirred with (1-pyrenyl)bromoalkane **1a-b** in THF at 60 °C for 18 h. After this time, the reaction mixture was cooled to room temperature and the precipitate was filtered under vacuum, washed with THF and then Et<sub>2</sub>O to afford the desired pyrene stabiliser BPS, LBPS or MPS.


### Liquid-Phase Exfoliation

To compare the exfoliation efficiency of BPS, MPS and LBPS, the graphene dispersions were prepared with the same initial stabiliser concentration (0.4 mg/mL). **Figure 1(a)** shows that a graphene concentration of 0.72 mg/mL was achieved by BPS, against 0.28 mg/mL obtained with MPS and 0.06 mg/mL with LBPS. The higher exfoliation efficiency of BPS compared to MPS is attributed to the presence of two pyrene binding groups, which improves the  $\pi$ - $\pi$  interactions between the molecules and graphene, and also affects the solubility of BPS in water (details in SI), driving the BPS molecules to minimize their interaction with water by adsorbing on graphene. It is interesting to note that the concentration obtained with MPS is comparable to that obtained by PS1 (**Figure 1(a)**), possibly because the two molecules have relatively good





solubility (details in SI) and a similar structure. Remarkably, LBPS, which also has two pyrene binding groups and is also insoluble in water, showed almost negligible exfoliation efficiency (Figure 1 (a)). This could be attributed to the different ways that these molecules are expected to assemble on graphene. The long chain connecting the pyrene binding groups in LBPS gives rise to some conformational freedom for the two pyrene binding groups, which may result in disruption of the controlled adsorption of the LBPS molecules due to possible interaction between the two pyrene bases. In the case of BPS, due to the relatively short carbon linking chain between the pyrene binding group and the functional group, the BPS molecule is more rigid, allowing more controlled assembly of BPS on graphene as well as adsorption of both the pyrene binding groups, exposing the charged functional group towards the water solvent. Alternatively, the poorer exfoliation efficiency of MPS could be attributed to intramolecular  $\pi$ - $\pi$  stacking of the molecules in solution.

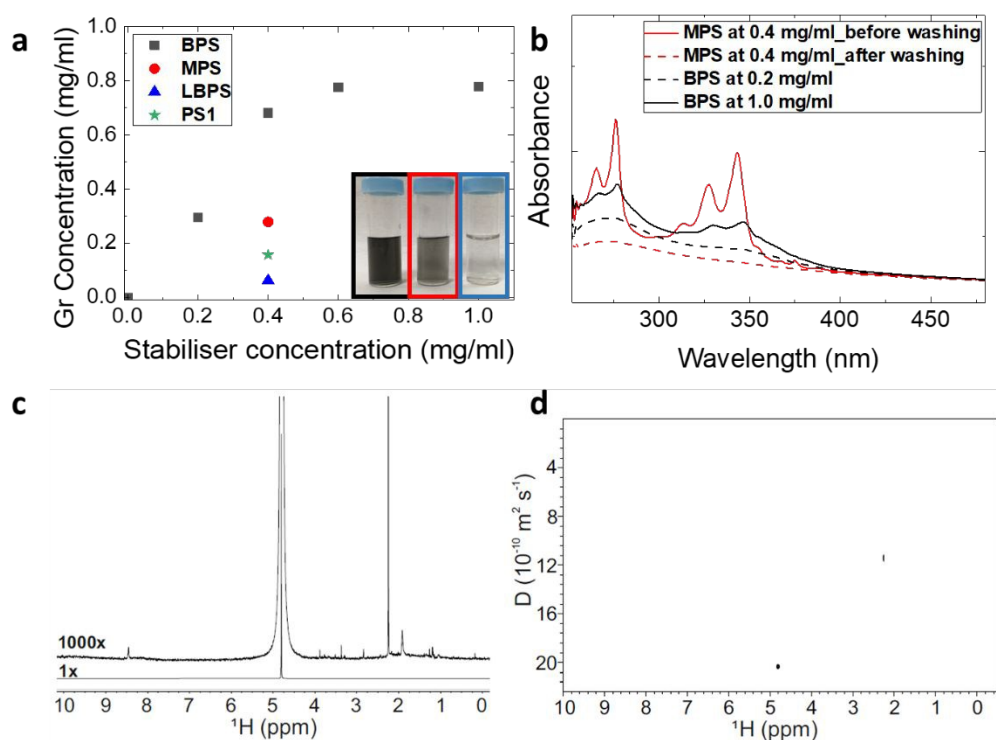

**Figure 1** (a) Graphene concentrations obtained for different graphene dispersions. inset: photographs of graphene dispersions prepared with different stabilisers, from left to right, BPS, MPS and LBPS at 0.4 mg/mL, all diluted by factor of 10. (b) UV-vis spectra of selected graphene dispersions with different pyrene concentrations. (c) Standard  $^1\text{H}$  spectrum of a graphene dispersion that was produced with an initial BPS concentration of 0.6 mg/mL in  $\text{D}_2\text{O}$



at 1x and 1000x magnifications. **(d)** 2D DOSY spectrum of a graphene dispersion that was produced with an initial BPS concentration of 0.6 mg/mL in D<sub>2</sub>O.

View Article Online  
DOI: 10.1039/C9FD00114J

The stability of graphene dispersions was estimated by measuring the zeta potential at ambient conditions. Typically, aqueous suspensions with  $|\zeta| > 30$  mV are regarded as stable suspensions.<sup>28</sup> The zeta potential of all the dispersions prepared in this study are between 30 and 50 mV, indicating very good stability (**Table 1** and **Figure S2**).

The enhanced exfoliation efficiency of BPS is attributed to the ability of these molecules to adsorb better on graphene. This is also supported by the observed trend of increasing concentration of the exfoliated graphene with increasing initial BPS concentration, reaching saturation above 0.4 mg/mL of BPS (**Figure 1 (a)** and **Figure S1**). UV-vis spectroscopy, in particular, shows clear BPS residual peaks, **Figure 1 (b)**. It is interesting to compare the spectrum obtained with BPS and MPS. Note that for better comparison of the intensities of the absorbance peaks of pyrene in the region between 250 nm and 400 nm, the spectra have been normalised against graphene absorbance at 660 nm. The prominent pyrene absorption peak in the dispersions obtained by MPS can easily be removed by a washing step (see Method), leaving no residual pyrene peaks in the UV-Vis spectrum after washing. In the case of BPS, however, there was no noticeable change of absorbance in that region after the washing step (**Figure S3**). As BPS is insoluble, this signal can only be attributed to the BPS adsorbed on the nanosheets. Furthermore, as shown in **Figure 1(b)**, an increase in pyrene absorbance is observed with increasing initial PBS concentration, which should be attributed to the increased amount of BPS molecules adsorbed on the graphene surface.

In order to confirm that all BPS molecules are adsorbed on graphene, we performed 1D and DOSY <sup>1</sup>H NMR experiments. DOSY uses measurements of diffusion to enable the separation of the NMR signals of different components in a mixture, and can be used to probe interactions between components.<sup>36,37</sup> Initially, a standard <sup>1</sup>H spectrum of a graphene dispersion with a BPS concentration of 0.6 mg/mL was collected, shown in **Figure 1(c)**. This spectrum is dominated by the 0.2% of protons present in the D<sub>2</sub>O used and no pyrene aromatic signals are seen. The DOSY spectrum of **Figure 1(d)** shows only the signals of rapidly diffusing water and trace acetone. No free BPS is detected, indicating that the pyrene present is tightly bound to the graphene nanosheets, which tumble slowly in solution, and hence shows rapid spin-spin relaxation. A wide <sup>1</sup>H spectrum (**Figure S4**) confirmed that most of the <sup>1</sup>H signal intensity comes from very broad signals.



### Characterisation of the exfoliated graphene nanosheets

Three graphene dispersions (BPS at 0.4 mg/mL, BPS at 0.6 mg/mL and MPS at 0.4 mg/mL) were chosen for further characterisation of the exfoliated graphene flakes by Raman spectroscopy, AFM and TEM. Supernatants collected for the two BPS dispersions were also characterised for comparison. Note that higher exfoliation yield is not necessarily an indication of a higher percentage of single layers, hence further characterisation is mandatory. The results are summarised in **Table 1**.

	BPS at 0.4 mg/mL	BPS at 0.6 mg/mL	MPS at 0.4 mg/mL
Concentration of dispersion ( <i>mg/mL</i> )	0.72	0.78	0.28
Concentration of supernatant ( <i>mg/mL</i> )	0.06	0.06	/
Zeta potential of dispersion ( <i>mV</i> )	40	38	39
Zeta potential of supernatant ( <i>mV</i> )	47	40	/
%SLG of dispersion	~58%	~44%	16%
%SLG of supernatant	~90%	~97%	/
Av. flake size of dispersion ( <i>nm</i> )	124	121	230
Av. flake size of supernatant ( <i>nm</i> )	44	50	/

**Table 1** Summary of the properties of the selected graphene dispersions and related supernatants.

Raman spectroscopy is the most commonly used characterization tool for graphene.<sup>38</sup> The Raman spectrum of graphene is characterized by the G, D and 2D peaks, lying at  $\sim 1580\text{ cm}^{-1}$ ,  $\sim 1350\text{ cm}^{-1}$ , and  $2680\text{ cm}^{-1}$ , respectively. In the case of graphene produced by LPE, which typically has size smaller than 500 nm, the D peak is activated by the edges of the nanosheets<sup>39</sup>, thus the intensity ratio between D and G peaks,  $I(D)/I(G)$ , changes with the size of the flakes.<sup>13,26,27,33</sup> The 2D peak shape is typically used to identify single layer graphene.<sup>40</sup> However, this identification method cannot be applied with the same accuracy to graphene produced by LPE, as the shape of the 2D peak is affected by edge effects, solvent or stabiliser doping and/or re-stacking of flakes.<sup>21,41</sup> Here we performed a qualitative thickness analysis using a protocol developed and tested in our group, based on Lorentzian fitting of the 2D peak (details in the Methods section).<sup>13,26,27,33,34</sup> **Figure 2 (a)** shows representative graphene Raman spectra obtained from the BPS at 0.6 mg/mL dispersion and supernatant. The Raman analysis shows that BPS is highly efficient at exfoliating graphene: both the BPS dispersions had a SLG percentage between 40 and 60%, compared to 16% measured for the MPS dispersion. Thus, BPS gives high exfoliation yield, as well as a high percentage of single and few layers,



compared to traditional pyrene derivatives. Moreover, **Figure 2 (a)** shows that the flakes in the supernatant are characterised by higher  $R^2$  value as well as higher  $I(D)/I(G)$ . Thus, the supernatant is expected to contain thinner flakes, mostly single-layers and of smaller size, compared to the dispersion. This is confirmed by AFM, **Figure 2 (c) and (d)**. These figures show the lateral size distribution for the dispersion and supernatant of BPS at 0.6 mg/mL (AFM images used for statistical analysis and the distribution histograms for the other samples are shown in the SI). AFM results show that the average flake size of the two BPS dispersions is centered at  $\sim 125$  nm, slightly smaller than that of the flakes in the MPS dispersion, which is peaked at  $\sim 230$  nm, in agreement with previous studies reporting graphene dispersions prepared with pyrene derivatives.<sup>4,11,21,29</sup> The average flake size of the two supernatant dispersions obtained with BPS was about  $\sim 50$  nm, which is expected, as smaller and thinner flakes are likely to be found in the supernatant. Note that with traditional pyrene derivatives, the concentration of graphene in the supernatant is too small, typically below 0.01 mg/mL, for further use; in contrast, LPE with BPS offers a very simple way to achieve concentrated and enriched graphene dispersions, although of much reduced flake size.


Thickness distributions obtained by AFM (**Figure S5 and S6**) confirm the Raman analysis, showing that BPS dispersions contain a higher number of thinner flakes than dispersions made with MPS. However, the thickness distribution obtained by AFM should be viewed with caution as the adsorption of stabilisers and solvent molecules on the surface of graphene flakes leads to higher thicknesses than those theoretically expected.<sup>21,42,43</sup> Because of this, the BPS at 0.6 mg/mL sample was further characterised by TEM. **Figure 3 (a)** shows the lateral size distribution histogram obtained from TEM analysis, which is in good agreement with that obtained from AFM (**Figure 2(c)**).

**Figure 3(b)** shows the thickness distribution histogram, collected for statistical analysis of more than 200 individual flakes: the dispersion is mostly composed of thin ( $< 10$  layers) flakes. It should be noted that the discrepancy between the SLG percentages estimated by Raman and by TEM analysis is attributable to the different sample preparation: the Raman sample was prepared by drop casting on silicon wafer whereas TEM sample was prepared by dip-coating on lacy carbon grid. However, despite the discrepancy, both techniques show that the graphene dispersion prepared with BPS is well exfoliated, mostly containing thin layers, as further confirmed in **Figure 3(c) and (d)**.

### Biocompatibility study




Previous work from our group<sup>4</sup> has shown that graphene flakes prepared by LPE with PS1 are highly biocompatible, with no cytotoxicity observed for concentrations up to 100  $\mu\text{g}/\text{mL}$ . It is, however, unclear if and how the cytotoxicity is related to the type of pyrene derivative used. Thus, here we compare the cytotoxicity of the dispersions obtained with MPS and BPS, which have the same functional group, but different numbers of pyrene binding groups. As the nanosheets of the graphene dispersions produced by BPS and MPS have comparable size, the comparison of cytotoxicity between the two samples allows the effect of the stabiliser, which determines the surface chemistry, on cellular interactions to be determined.

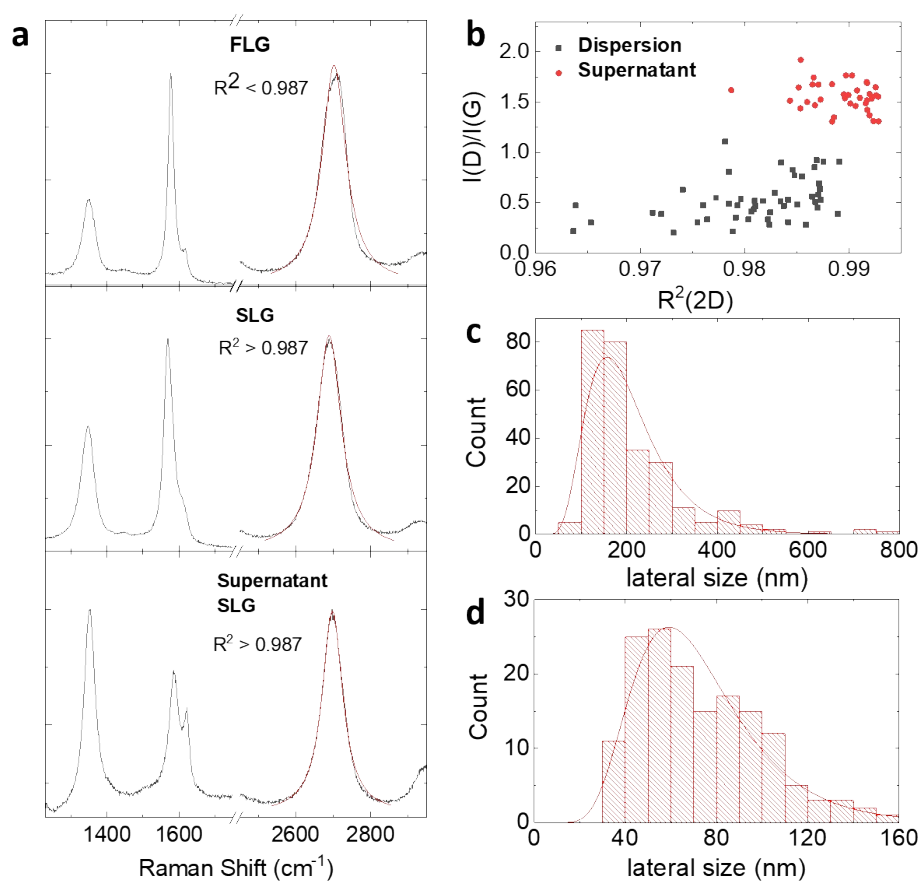

**Figure 2** Characterisation of graphene dispersion prepared with BPS at 0.6 mg/mL. **(a)** Representative Raman spectra taken from the dispersion and the supernatant of BPS at 0.6 mg/mL. The fit of the 2D peak is also shown (red line) **(b)**  $I(D)/I(G)$  vs fit residual of the 2D peak plot for both dispersions and supernatant samples. **(c)** and **(d)** Lateral size distribution histograms measured by AFM for dispersion and supernatant samples, respectively.



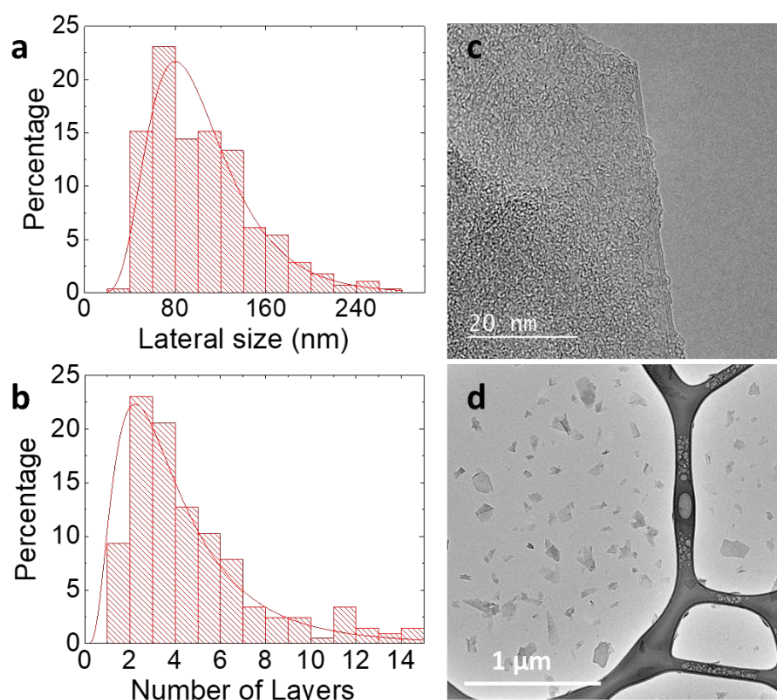

View Article Online  
DOI: 10.1039/C9FD00114J

**Figure 3** TEM characterisation of graphene dispersion prepared with BPS at 0.6 mg/mL: **(a)** lateral size and **(b)** thickness distribution, **(c)** HRTEM image of a three-layer-thick graphene flake and **(d)** overview TEM image of graphene flakes.


To establish a cytotoxicity profile, optical microscopy was used with BEAS-2B cell lines as an immortalised *in vitro* model for four different graphene dispersions prepared in this study: three graphene dispersions prepared with BPS (BPS at 0.2 mg/mL, BPS at 0.6 mg/mL, BPS at 1.0 mg/mL to determine the effect of BPS concentration), and one graphene dispersion prepared with MPS (MPS at 0.4 mg/mL). Cells were exposed to increasing concentrations of graphene, from 25  $\mu\text{g/mL}$  to 100  $\mu\text{g/mL}$ . As a control, untreated cells were also observed (**Figure 4, top left panel**)

**Figure 4** shows the optical images of the cells exposed to graphene flakes and morphological changes/cellular detachment, as indicators of cell death. **Figure 4** clearly shows that the cytotoxicity of graphene flakes increases with increasing concentration of BPS. No noticeable changes in cell morphology was observed for BPS at 0.2 mg/mL at any of graphene concentrations used. However, for BPS at 0.6 mg/mL, at 25  $\mu\text{g/mL}$  the appearance of the vesicles indicated cellular stress and lysosomal swelling. Dose dependent toxic effects on the cells were also observed, as at 75  $\mu\text{g/mL}$ , rounding of the cells is apparent, indicating apoptotic cell death as well as detachment of dead cells from the support. As expected, highly stressed cells were observed using BPS at 1.0 mg/mL even at the lowest concentration of 25  $\mu\text{g/mL}$




(high numbers of vesicles appearing in the cells), while cell death and detachment from the support occurred at 50  $\mu\text{g/mL}$  BPS at 1.0  $\text{mg/mL}$ .

View Article Online  
DOI: 10.1039/C9FD00114J

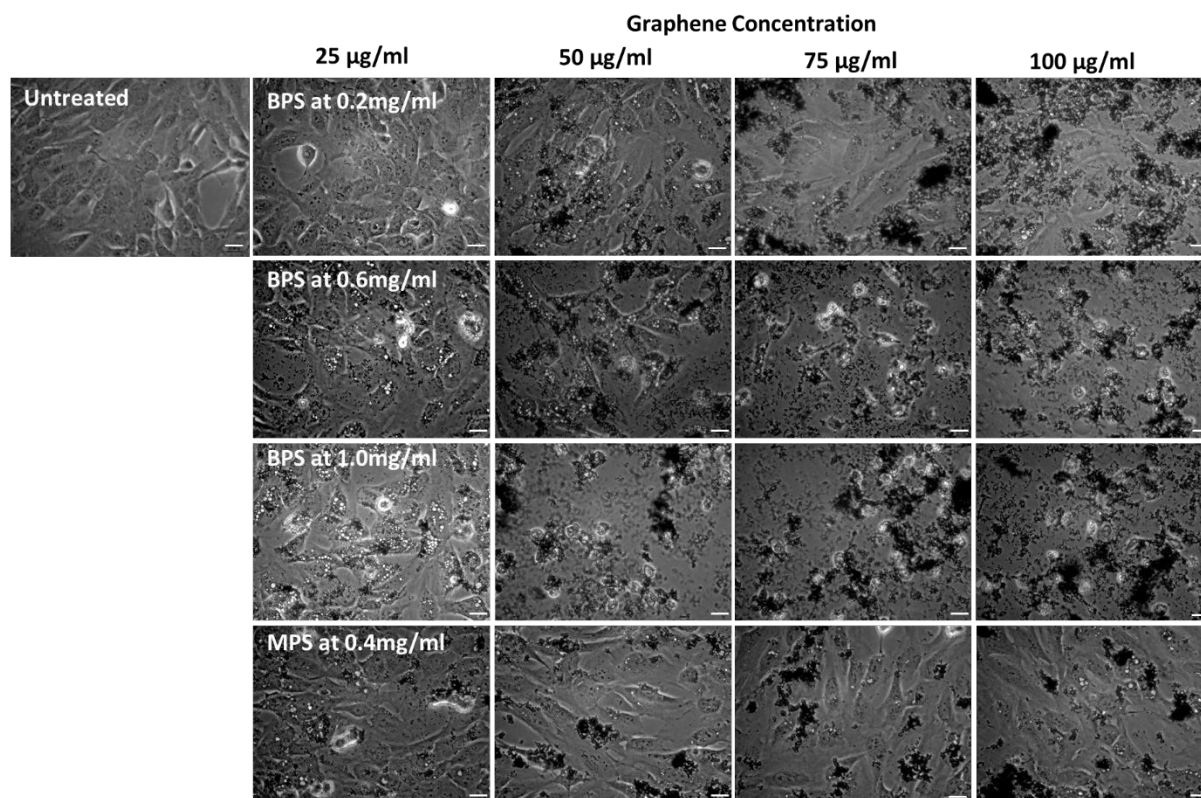

**Figure 4** Optical images of BEAS-2B cells, exposed to 4 different graphene dispersions, BPS at 0.2  $\text{mg/mL}$ , BPS at 0.6  $\text{mg/mL}$ , BPS at 1.0  $\text{mg/mL}$ , MPS at 0.4  $\text{mg/mL}$ , at 4 different concentrations, 25  $\mu\text{g/mL}$ , 50  $\mu\text{g/mL}$ , 75  $\mu\text{g/mL}$ , and 100  $\mu\text{g/mL}$ . Cells were observed for morphological changes and loss of viability indicated by detachment from the support, in comparison to untreated cells. Scale bar is 10  $\mu\text{m}$ .

On the other hand, cells exposed to MPS at 0.4  $\text{mg/mL}$  showed no evident morphological changes or detachment from the support, with few vesicles appearing inside the cells, demonstrating good biocompatibility at high graphene concentration (100  $\mu\text{g/mL}$ ) after 24 h of treatment.

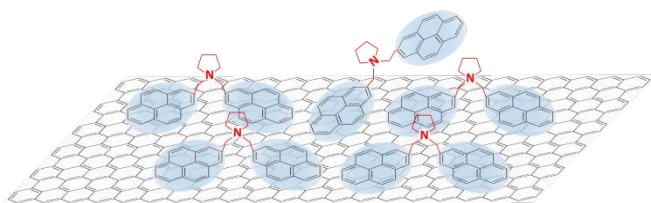

**Figure 5** Possible adsorption of BPS at high concentration, giving rise to higher graphene cytotoxicity, compared to MPS.



These results clearly demonstrate the cytotoxic effect of BPS. The simplest explanation is to attribute the higher cytotoxicity to the higher number of molecules adsorbed (Figure 1b). However, it is interesting to note that BPS and MPS are characterised by the same functional group interacting with the cells, but graphene produced by MPS does not show any cytotoxicity even at high concentrations. Thus, a more complex scenario may be possible. In the case of soluble MPS, not all stabiliser is adsorbed on graphene, and the free MPS molecules in water are removed during the washing steps. In the case of the insoluble BPS, the stabiliser needs to be adsorbed on graphene. However, after a certain BPS concentration, the graphene surface could reach complete coverage. As these molecules are insoluble, they will still want to interact with graphene and therefore may accommodate on its surface by adopting a frustrated configuration, in which only one pyrene binding group is adsorbed on graphene. As the other pyrene group is now exposed to the water, this reflects in an effective increase in concentration of pyrene accessible to cells in solution at high BPS concentrations (Figure 5), giving rise to a higher cytotoxic effect, compared to the case of MPS molecules. However, this would not affect graphene concentration, as there are enough BPS molecules completely adsorbed on graphene, by providing electrostatic stabilization. Alternatively, the molecules may start interacting with each other, forming large aggregates on graphene, which may affect the cytotoxicity. Further study is required to fully understand the exact mechanism of the increased cytotoxicity observed with BPS molecules.

## Conclusion

In summary, we have demonstrated the use of an insoluble stabiliser to achieve highly concentrated aqueous graphene dispersions, mostly containing single or few layer flakes. Although their use in biomedical applications is limited by their reduced biocompatibility, these graphene dispersions are still suitable for many applications, where water is the preferred solvent. Our work also shows that LPE of graphene can be used to disperse insoluble molecules in water, as graphene and the hydrophobic side of the molecules self-assemble together to minimize interactions with water molecules, similarly to micellization

## Acknowledgements

This work was supported by the EPSRC in the framework of the project 2D Health (EP/P00119X/1). MB acknowledges financial support by the European Research Council (ERC) in the framework of the European Union's Horizon 2020 research and innovation program under the grant agreement No. 648471. MZ acknowledges the Hewlett-Packard

View Article Online  
DOI: 10.1039/C9FD00114J





Company for financial support in the framework of the Graphene NowNano Doctoral Training Center.

View Article Online  
DOI: 10.1039/C9FD00114J

### Contribution statement

CC, IL, and KK conceived and supervised the project. YY and MB performed the exfoliation experiments and related data analysis. AP and XJ-B made the pyrene derivatives and performed their characterization. YC and SV performed the biological studies and related data analysis. XL and EP performed the electron microscopy measurements and related data analysis. GM performed DOSY NMR and related data analysis. MZ performed AFM measurements and related data analysis. The manuscript was written with contributions from all authors.



## References

1. Novoselov, K. S. *et al.* A roadmap for graphene. *Nature* **490**, 192–200 (2012).
2. Hernandez, Y. *et al.* High-yield production of graphene by liquid-phase exfoliation of graphite. *Nat. Nanotechnol.* **3**, 563–568 (2008).
3. Nicolosi, V., Chhowalla, M., Kanatzidis, M. G., Strano, M. S. & Coleman, J. N. Liquid Exfoliation of Layered Materials. *Science*. **340**, 1226419–1226419 (2013).
4. McManus, D. *et al.* Water-based and biocompatible 2D crystal inks for all-inkjet-printed heterostructures. *Nat. Nanotechnol.* **12**, 1–19 (2017).
5. Coleman, J. N. Liquid exfoliation of defect-free graphene. *Acc. Chem. Res.* **46**, 14–22 (2013).
6. Ferrari, A. C. *et al.* Science and technology roadmap for graphene, related two-dimensional crystals, and hybrid systems. *Nanoscale* **7**, 4598–4810 (2015).
7. Ciesielski, A. & Samori, P. Supramolecular Approaches to Graphene: From Self-Assembly to Molecule-Assisted Liquid-Phase Exfoliation. *Adv. Mater.* **28**, 6030–6051 (2016).
8. Loh, K. P., Bao, Q., Eda, G. & Chhowalla, M. Graphene oxide as a chemically tunable platform for optical applications. *Nat. Chem.* **2**, 1015–1024 (2010).
9. Lotya, M. *et al.* Liquid phase production of graphene by exfoliation of graphite in surfactant/water solutions. *J. Am. Chem. Soc.* **131**, 3611–3620 (2009).
10. Parviz, D. *et al.* Dispersions of non-covalently functionalized graphene with minimal stabilizer. *ACS Nano* **6**, 8857–8867 (2012).
11. Schlierf, A. *et al.* Nanoscale insight into the exfoliation mechanism of graphene with organic dyes: effect of charge, dipole and molecular structure. *Nanoscale* **5**, 4205 (2013).
12. Lotya, M., King, P. J., Khan, U., De, S. & Coleman, J. N. High-concentration, surfactant-stabilized graphene dispersions. *ACS Nano* **4**, 3155–3162 (2010).
13. Haar, S. *et al.* Enhancing the Liquid-Phase Exfoliation of Graphene in Organic Solvents upon Addition of n-Octylbenzene. *Sci. Rep.* **5**, 16684 (2015).
14. Hernandez, Y., Lotya, M., Rickard, D., Bergin, S. D. & Coleman, J. N. Measurement of multicomponent solubility parameters for graphene facilitates solvent discovery. *Langmuir* **26**, 3208–3213 (2010).
15. Villar-Rodil, S., Paredes, J. I., Martínez-Alonso, A. & Tascón, J. M. D. Preparation of graphene dispersions and graphene-polymer composites in organic media. *J. Mater. Chem.* **19**, 3591 (2009).
16. May, P., Khan, U., Hughes, J. M. & Coleman, J. N. Role of solubility parameters in understanding the steric stabilization of exfoliated two-dimensional nanosheets by adsorbed polymers. *J. Phys. Chem. C* **116**, 11393–11400 (2012).
17. Xu, L. *et al.* Production of high-concentration graphene dispersions in low-boiling-point organic solvents by liquid-phase noncovalent exfoliation of graphite with a hyperbranched polyethylene and formation of graphene/ethylene copolymer composites. *J. Phys. Chem. C* **117**, 10730–10742 (2013).
18. Ghosh, A., Rao, K. V., George, S. J. & Rao, C. N. R. Noncovalent Functionalization, Exfoliation, and Solubilization of Graphene in Water by Employing a Fluorescent Coronene Carboxylate. *Chem. - A Eur. J.* **16**, 2700–2704 (2010).
19. Englert, J. M. *et al.* Soluble Graphene: Generation of Aqueous Graphene Solutions Aided by a Perylenebisimide-Based Bolaamphiphile. *Adv. Mater.* **21**, 4265–4269 (2009).
20. Amiri, A., Naraghi, M., Ahmadi, G., Soleymaniha, M. & Shanbedi, M. A review on liquid-phase exfoliation for scalable production of pure graphene, wrinkled, crumpled



- and functionalized graphene and challenges. *FlatChem* **8**, 40–71 (2018).
21. Yang, H. *et al.* A simple method for graphene production based on exfoliation of graphite in water using 1-pyrenesulfonic acid sodium salt. *Carbon*. **53**, 357–365 (2013). View Article Online  
DOI: 10.1039/C9FD00114J
  22. Lee, D. W., Kim, T. & Lee, M. An amphiphilic pyrene sheet for selective functionalization of graphene. *Chem. Commun.* **47**, 8259–8261 (2011).
  23. Zhang, M. *et al.* Production of graphene sheets by direct dispersion with aromatic healing agents. *Small* **6**, 1100–1107 (2010).
  24. Yang, H. *et al.* Dielectric nanosheets made by liquid-phase exfoliation in water and their use in graphene-based electronics. *2D Mater.* **1**, 011012 (2014).
  25. Heard, K. W. J. *et al.* Initial Studies Directed toward the Rational Design of Aqueous Graphene Dispersants. *ACS Omega* **4**, 1969–1981 (2019).
  26. Conti, S. *et al.* Perchlorination of Coronene Enhances its Propensity for Self-Assembly on Graphene. *ChemPhysChem* **17**, 352–357 (2016).
  27. Haar, S. *et al.* A supramolecular strategy to leverage the liquid-phase exfoliation of graphene in the presence of surfactants: Unraveling the role of the length of fatty acids. *Small* **11**, 1691–1702 (2015).
  28. Smith, R. J., Lotya, M. & Coleman, J. N. The importance of repulsive potential barriers for the dispersion of graphene using surfactants. *New J. Phys.* **12**, (2010).
  29. Shin, Y. *et al.* Charge-tunable graphene dispersions in water made with amphoteric pyrene derivatives. *Mol. Syst. Des. Eng.* (2019). doi:10.1039/C9ME00024K
  30. Bonaccorso, F. *et al.* Production and processing of graphene and 2d crystals. *Mater. Today* **15**, 564–589 (2012).
  31. Khan, U., O'Neill, A., Lotya, M., De, S. & Coleman, J. N. High-concentration solvent exfoliation of graphene. *Small* **6**, 864–871 (2010).
  32. Hunter, R. J. *Zeta potential in colloid science : principles and applications. Colloid science* **2**, (Academic Press, 1981).
  33. Ciesielski, A. *et al.* Harnessing the Liquid-Phase Exfoliation of Graphene Using Aliphatic Compounds: A Supramolecular Approach. *Angew. Chemie Int. Ed.* **53**, 10355–10361 (2014).
  34. Shin, Y. *et al.* Synthesis and characterization of composite membranes made of graphene and polymers of intrinsic microporosity. *Carbon N. Y.* **102**, 357–366 (2016).
  35. Pelta, M. D., Morris, G. A., Stchedroff, M. J. & Hammond, S. J. A one-shot sequence for high-resolution diffusion-ordered spectroscopy. *Magn. Reson. Chem.* **40**, S147–S152 (2002).
  36. Johnson, C. S. Diffusion ordered nuclear magnetic resonance spectroscopy: principles and applications. *Prog. Nucl. Magn. Reson. Spectrosc.* **34**, 203–256 (1999).
  37. Bichenkova, E. V *et al.* NMR detects molecular interactions of graphene with aromatic and aliphatic hydrocarbons in water. *2D Mater.* **5**, 15003 (2017).
  38. Jorio, A., Saito, R., Dresselhaus, G. & Dresselhaus, M. S. *Raman Spectroscopy in Graphene Related Systems. Raman Spectroscopy in Graphene Related Systems* (2011). doi:10.1002/9783527632695
  39. Casiraghi, C. *et al.* Raman spectroscopy of graphene edges. *Nano Lett.* **9**, 1433–1441 (2009).
  40. Ferrari, A. C. *et al.* Raman spectrum of graphene and graphene layers. *Phys. Rev. Lett.* **97**, 1–4 (2006).
  41. Carozo, V. *et al.* Resonance effects on the Raman spectra of graphene superlattices. *Phys. Rev. B - Condens. Matter Mater. Phys.* **88**, 1–10 (2013).
  42. Paton, K. R. *et al.* Scalable production of large quantities of defect-free few-layer graphene by shear exfoliation in liquids. *Nat. Mater.* **13**, 624–630 (2014).



43. Backes, C. *et al.* Guidelines for Exfoliation, Characterization and Processing of Layered Materials Produced by Liquid Exfoliation. *Chem. Mater.* **29**, 243–255 (2017). View Article Online  
DOI: 10.1039/C9FD00114J

